

2

AD-A263 262



ARMY RESEARCH LABORATORY




# The Effect of Material Strength on Segment Penetration Behavior

Todd W. Bjerke

ARL-MR-51

April 1993

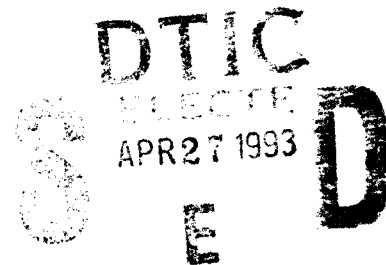

APPROVED FOR PUBLIC RELEASE; DISTRIBUTION IS UNLIMITED.

93 4 26 07 4

93-08905



23p8

REPORT DOCUMENTATION PAGE			Form Approved OMB No 0704-0188	
<small>Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.</small>				
1. AGENCY USE ONLY (Leave blank)		2. REPORT DATE April 1993		3. REPORT TYPE AND DATES COVERED Final, Jan 1992-Feb 1993
4. TITLE AND SUBTITLE  The Effect of Material Strength on Segment Penetration Behavior			5. FUNDING NUMBERS  PR: 1L162618AH80	
6. AUTHOR(S)  Todd W. Bjerke				
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES)  U.S. Army Research Laboratory ATTN: AMSRL-WT-TC Aberdeen Proving Ground, MD 21005-5066			8. PERFORMING ORGANIZATION REPORT NUMBER	
9. SPONSORING / MONITORING AGENCY NAME(S) AND ADDRESS(ES)  U.S. Army Research Laboratory ATTN: AMSRL-OP-CI-B (Tech Lib) Aberdeen Proving Ground, MD 21005-5066			10. SPONSORING / MONITORING AGENCY REPORT NUMBER  ARL-MR-51	
11. SUPPLEMENTARY NOTES				
12a. DISTRIBUTION / AVAILABILITY STATEMENT  Approved for public release; distribution is unlimited.			12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words)  <p>The effects of penetrator material strength on the terminal ballistic behavior of tungsten alloy segments fired into armor plate was determined by a series of impact experiments. Three different strength tungsten alloys were machined into cylinders with an aspect ratio of 4 and were subsequently impacted into rolled homogeneous armor at 1.5 km/s. The depth of penetration and the shape of the penetrator material remaining in the penetration cavity were recorded and compared. Decreasing the penetrator material strength was observed to slightly decrease the length of residual material and the depth of penetration. The diameter of the plastically deformed residual material was observed to increase with decreasing penetrator material strength.</p>				
14. SUBJECT TERMS  terminal ballistics, tungsten alloys, armor plate, impact strength, armor piercing projectiles, plastic deformation, impact testing			15. NUMBER OF PAGES 20	
			16. PRICE CODE	
17. SECURITY CLASSIFICATION OF REPORT  UNCLASSIFIED	18. SECURITY CLASSIFICATION OF THIS PAGE  UNCLASSIFIED	19. SECURITY CLASSIFICATION OF ABSTRACT  UNCLASSIFIED	20. LIMITATION OF ABSTRACT  UL	

# TABLE OF CONTENTS

	<u>Page</u>
LIST OF FIGURES .....	v
ACKNOWLEDGMENTS .....	vii
1. INTRODUCTION .....	1
2. IMPACT EXPERIMENTS .....	1
3. IMPACT RESULTS .....	6
4. CONCLUSIONS .....	11
5. REFERENCES .....	13
LIST OF SYMBOLS .....	15
DISTRIBUTION LIST .....	17

Accession For	
NTIS CRA&I	<input checked="checked" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By	
Distribution	
Availability Codes	
Dist	Avail and/or Special
A-1	

## LIST OF FIGURES

<u>Figure</u>	<u>Page</u>
1. Cross section view of four petal sabot . . . . .	3
2. Residual material geometry description . . . . .	6
3. Recovered residual penetrators . . . . .	7
4. Normalized segment penetration vs. material strength . . . . .	9
5. Normalized total residual length vs. material strength . . . . .	9
6. Normalized length of shank and mushroom head vs. material strength . . . . .	10
7. Fraction of residual length plastically deformed vs. material strength . . . . .	10
8. Normalized mushroom head diameter and impact crater diameter vs. material strength . . . . .	11

## ACKNOWLEDGMENTS

The author acknowledges Ms. Lori Luther for her contributions towards this program, specifically for the photography and the proper disposition of targets. The author also acknowledges Mr. William Edmanson for his innovative technique for preventing the sabot pusher plates from impacting the targets.

## 1. INTRODUCTION

Segmented rod penetrator technology has emerged as a topic of interest to the terminal ballistic community due to the increase in normalized penetration performance ( $P/L$ ,  $P$  being depth of penetration and  $L$  being the compact penetrator length) against rolled homogeneous armor (RHA) targets. One of the factors which has hindered the performance of segmented rod penetrators at ordnance and slightly higher velocities has been the large length of residual segment material which does not erode and must be impacted by the next subsequent segment. Even at moderately high velocities (i.e., those in the 2-km/s regime), evidence exists that the residual segment material still impedes penetration (Hohler and Saip 1987; Raatschen et al. 1987; Orphal and Franzen 1989; Herbette 1989). Given this to be the case, it follows that segmented rod penetrator performance could be improved if the segment material was modified to reduce the residual length, but only if the same level of segment  $P/L$  is maintained. Fortunately, penetrator strength has been shown not to influence the penetration performance of tungsten alloy penetrators with length-to-diameter ( $L/D$ ) ratios ranging from 10 to 15 (Meyer, Behler, Frank, and Magness 1990). However, it is unknown if this is equally true for penetrators with much lower  $L/D$  ratios.

Typical materials used for segmented rod penetrators are tungsten alloys. One approach to possibly reduce the length of tungsten residual material is to reduce the compressive strength of the segment material. Fortunately, the tungsten alloys used can be processed such that a variety of strengths can be obtained. The experimental program documented within this report used three different strength tungsten alloys. Segments were machined from each of the three alloys to have a  $L/D$  ratio of 4, and each segment was impacted into semi-infinite RHA at a velocity of 1.5 km/s. Only one segment was impacted into each target. The residual segment material was removed from the target after impact, measured, and then compared.

## 2. IMPACT EXPERIMENTS

A total of six shots, consisting of two shots for each of the three different strength alloys, were made in the Army Research Laboratory (ARL) high-pressure gun facility. Details of the facility are given by Baur and Nagy (1979). The gun consists of a nominal 50-mm-dia by 6-m-travel smoothbore powder gun with a large-capacity, high-pressure powder chamber. The gun empties into an impact chamber at atmospheric pressure. The target was located approximately 4.8 m from the gun muzzle. One

Table 2. Penetrator Geometries

Shot No.	1% Comp. Yield (GPa)	Mass (g)	Diameter (mm)	Length (mm)
1	0.717	385.6	19.073	76.225
2	0.717	384.8	19.058	76.175
3	1.096	384.8	19.080	76.200
4	1.096	384.5	19.065	76.200
5	1.276	385.2	19.078	75.781
6	1.276	385.2	19.058	76.035

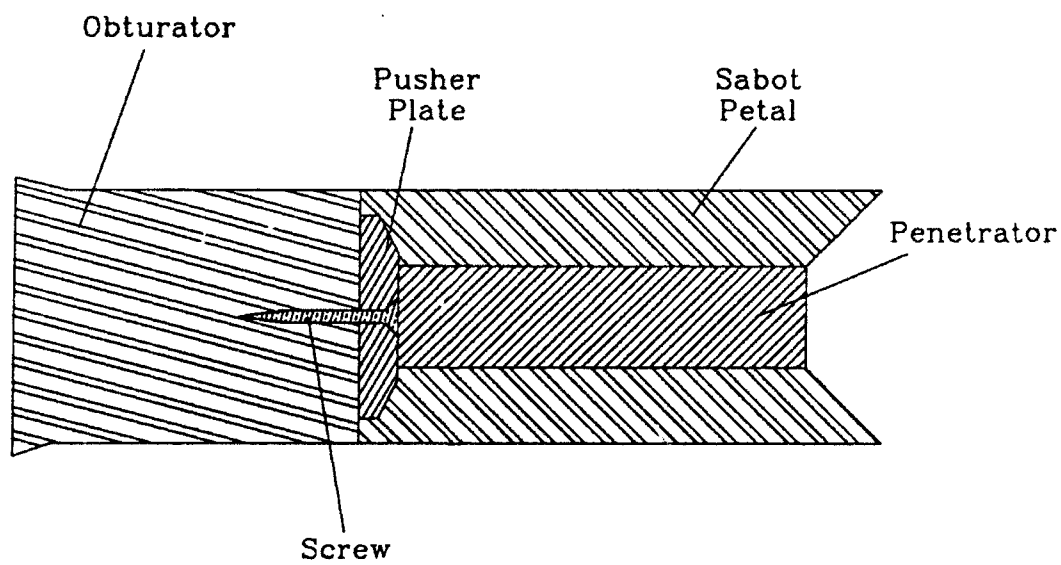


Figure 1. Cross section view of four-petal sabot.

Table 3. Results From Impact Experiments

Shot No.	1% Yield (GPa)	Velocity (km/s)	Yaw (deg)	L <sub>R</sub> (mm)	L <sub>H</sub> (mm)	L <sub>S</sub> (mm)	D <sub>H</sub> (mm)	D <sub>C</sub> (mm)	P (mm)
1	0.717	1.509	1.5	15.69	10.91	4.78	24.13	41.38	90.18
2	0.717	1.503	1.2	16.10	11.33	4.77	23.45	41.45	88.72
3	1.096	1.514	2.7	17.42	11.62	5.80	21.29	41.21	93.04
4	1.096	1.502	1.7	17.02	13.93	3.09	23.64	41.57	93.03
5	1.276	1.501	3.4	18.36	12.34	6.02	23.54	40.94	94.04
6	1.276	1.509	0.6	18.10	11.94	6.16	22.80	40.52	95.40



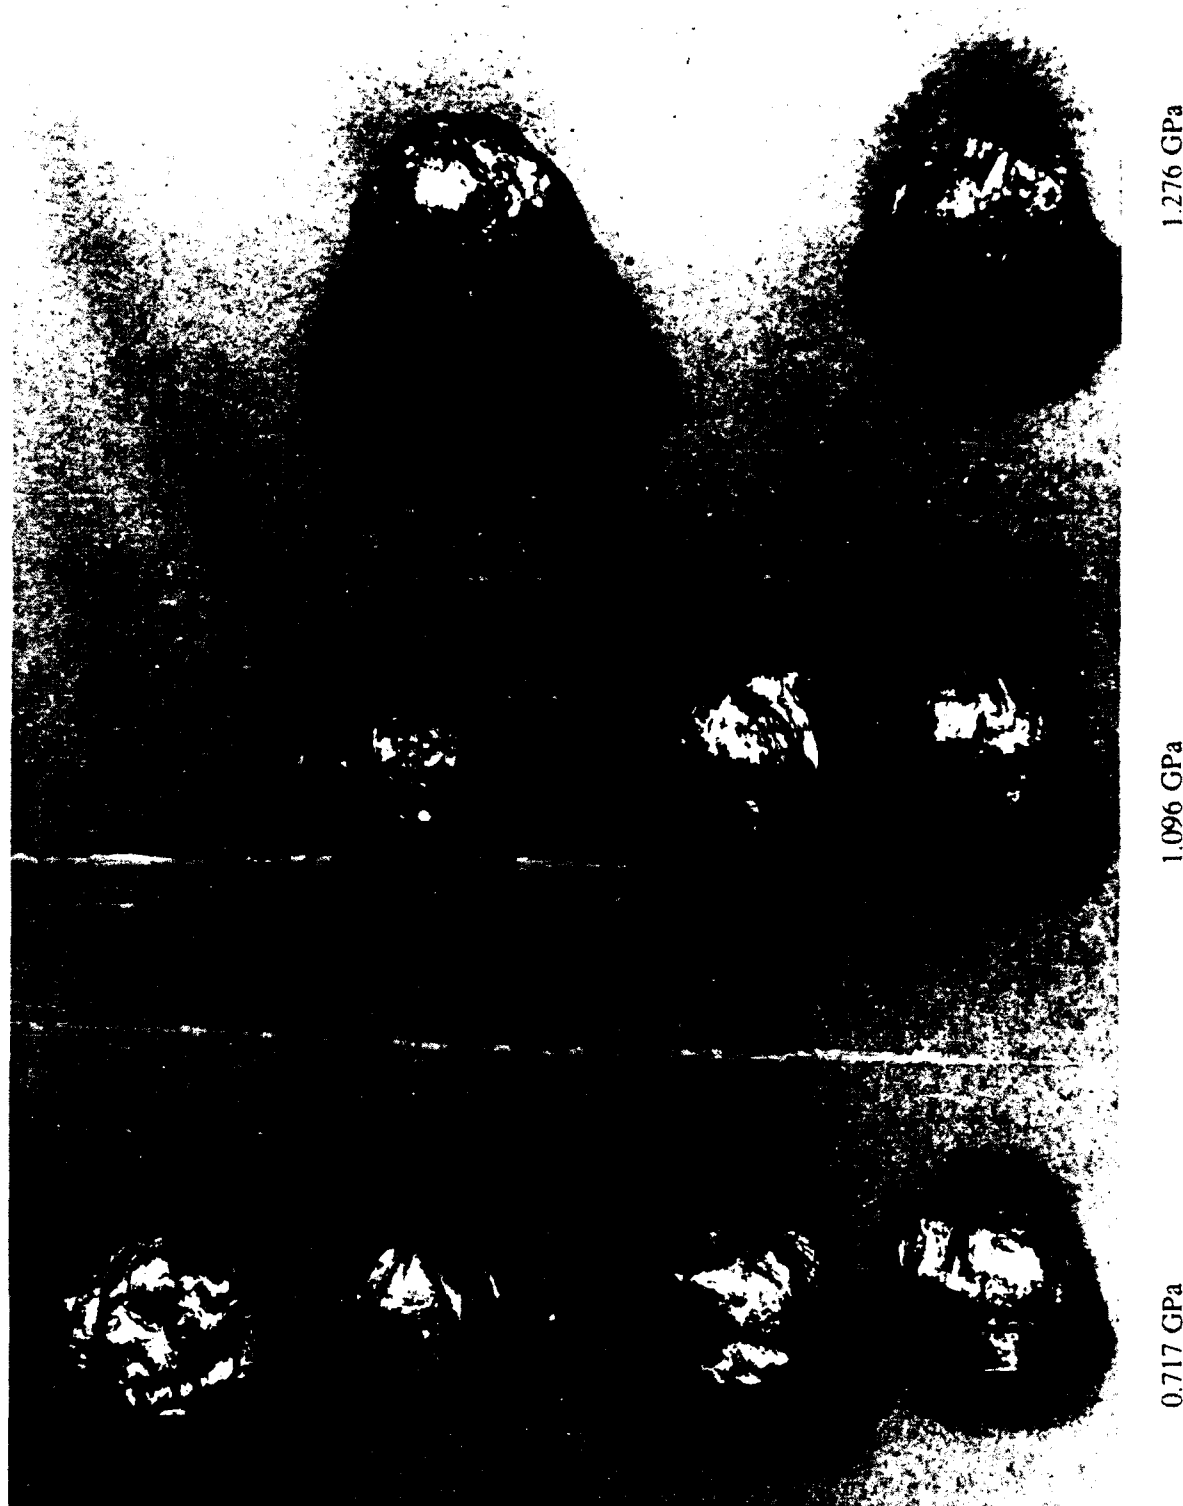


Figure 3. Recovered residual penetrators.

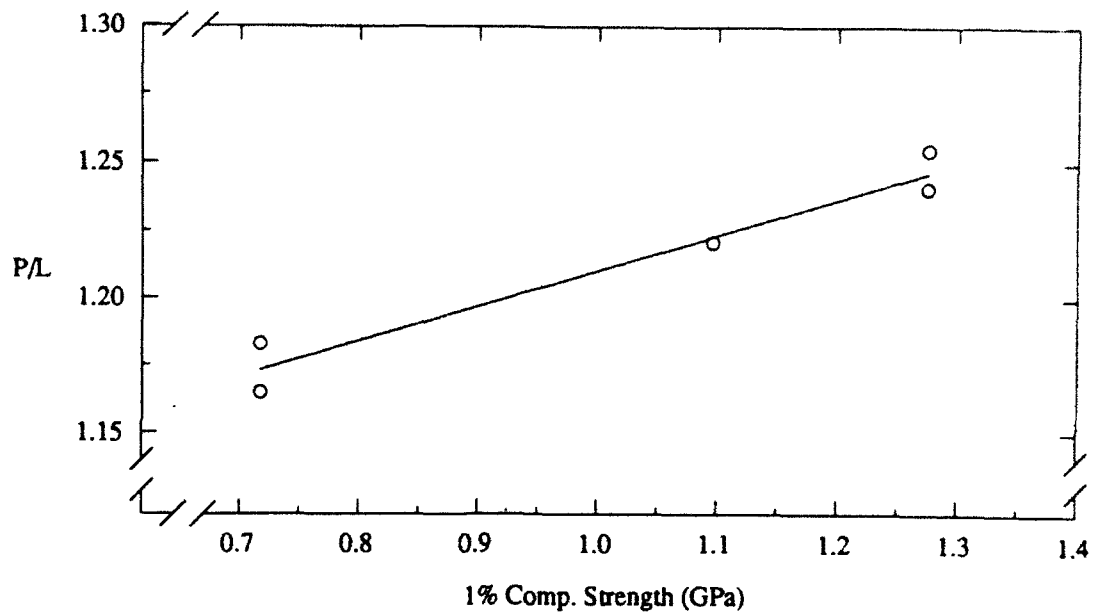


Figure 4. Normalized segment penetration vs. material strength.

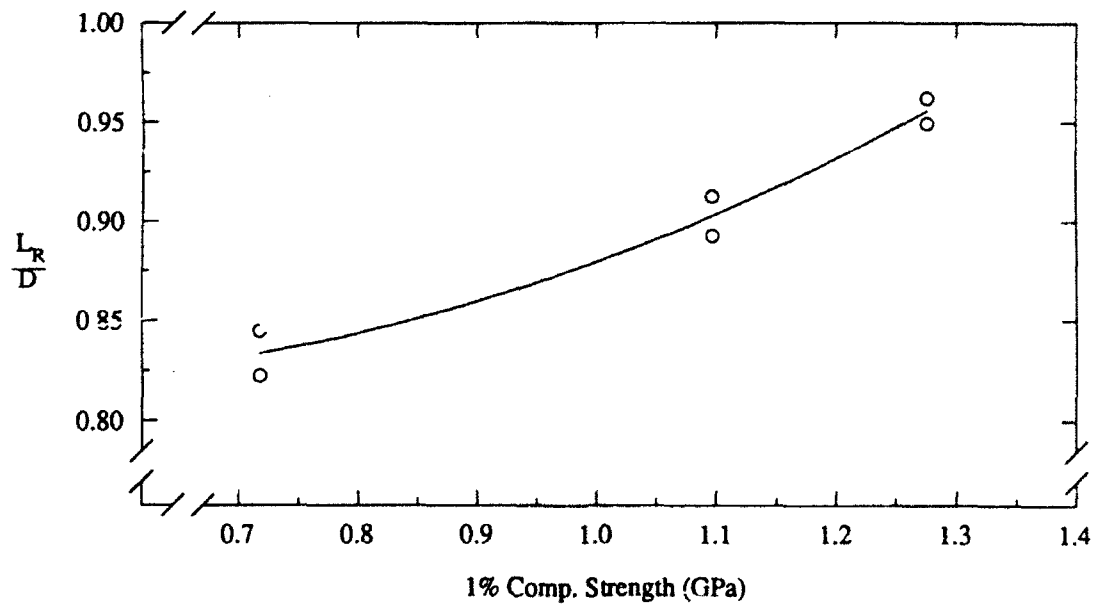


Figure 5. Normalized total residual length vs. material strength.

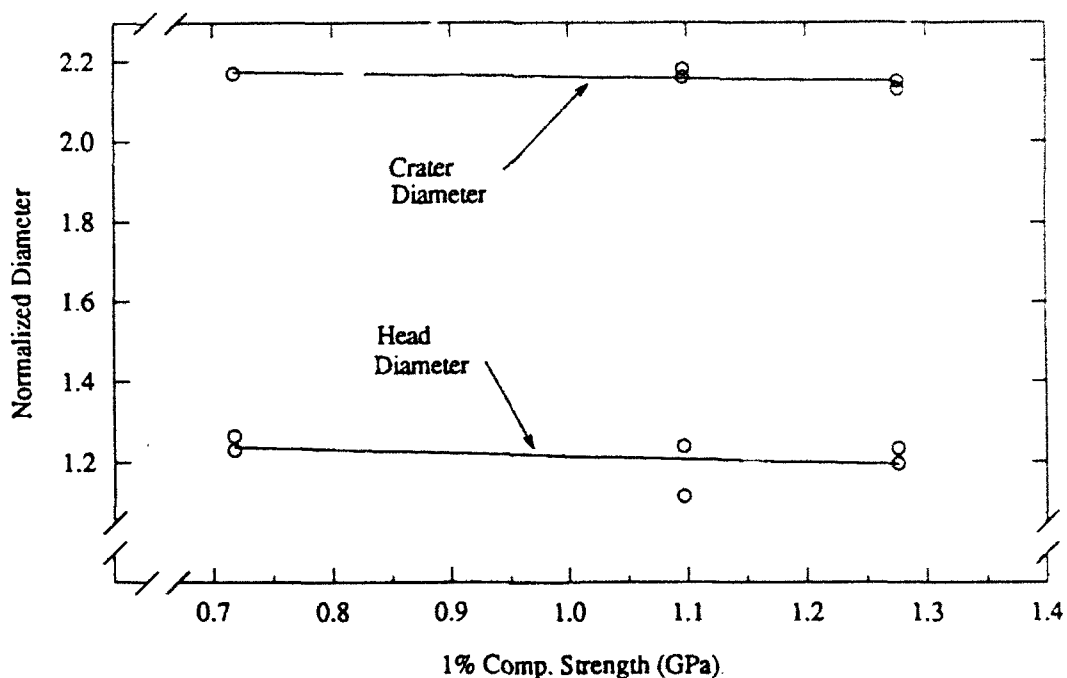


Figure 8. Normalized mushroom head diameter and impact crater diameter versus material strength.

#### 4. CONCLUSION

The modification of segment strength had a measurable (albeit small) effect on residual material length. Decreasing material strength resulted in a slight decrease in the length of residual material, while at the same time slightly increased the diameter of the mushroom head on the residual material and the percentage of residual length in the mushroom zone. This, in turn, resulted in an increase in the crater diameter and a decrease in the depth of penetration. The effect of penetrator strength on penetration performance differs from that observed for penetrators with higher  $L/D$  ratios. This discrepancy is most likely attributable to the fact that the penetration behavior of high  $L/D$  penetrators is primarily governed by hydrodynamic forces which do not depend upon material strength, whereas the behavior of low  $L/D$  penetrators is entirely transient and does depend upon material strength. Based on the observations of this study, it appears that segments made of softer material are more prone to plastically deform their material laterally than to move deeper into the target. Although the decrease in the residual length was measurable, the magnitude was sufficiently small to preclude this approach as a viable means for substantially improving the terminal ballistic performance of segmented rod penetrators. This is reinforced by the measured decrease in individual segment  $P/L$  which accompanied the decrease in residual length.

## 5. REFERENCES

- Baur, D. P., and M. D. Nagy. "Operation Manual for 50-mm Research Gun System." UDR-TR-79-80, University of Dayton Research Institute, Dayton, OH, October 1979.
- Herbette, G. "The Influence of Projectile Shape on Penetration Power." Proceedings of the 11th International Symposium on Ballistics, Brussels, Belgium, 1989.
- Hohler, V., and A. J. Stilp. "Hypervelocity Impact of Rod Projectiles with L/D from 1 to 32." International Journal of Impact Engineering, vol. 5, 1987.
- Meyer, L. W., F. J. Behler, K. Frank, and L. S. Magness. "Interdependencies Between the Dynamic Mechanical Properties and the Ballistic Behavior of Materials." Proceedings of the 12th International Symposium on Ballistics, San Antonio, Texas, 1990.
- Orphal, D. L., and R. R. Franzen. "Penetration Mechanics and Performance of Segmented Rods Against Metal Targets." International Journal of Impact Engineering, vol. 10, no. 1-4, December 1989.
- Raatschen, H. J., W. Pavel, S. Fuchs, H. Senf, and H. Rothenhausler. "Penetration Efficiency of Segmented Rods." Proceedings of the 11th International Symposium on Ballistics, Brussels, Belgium, 1987.

## LIST OF SYMBOLS

D	Original segment diameter, mm
D <sub>C</sub>	Impact crater entrance diameter, mm
D <sub>H</sub>	Segment mushroom head diameter, mm
L	Original segment length, mm
L <sub>H</sub>	Segment mushroom head length, mm
L <sub>R</sub>	Total residual segment material length, mm
L <sub>S</sub>	Shank length of residual segment material, mm
P	Depth of penetration, mm

<u>No. of Copies</u>	<u>Organization</u>	<u>No. of Copies</u>	<u>Organization</u>
2	Administrator Defense Technical Info Center ATTN: DTIC-DDA Cameron Station Alexandria, VA 22304-6145	1	Commander U.S. Army Missile Command ATTN: AMSMI-RD-CS-R (DOC) Redstone Arsenal, AL 35898-5010
1	Commander U.S. Army Materiel Command ATTN: AMCAM 5001 Eisenhower Ave. Alexandria, VA 22333-0001	1	Commander U.S. Army Tank-Automotive Command ATTN: ASQNC-TAC-DIT (Technical Information Center) Warren, MI 48397-5000
1	Director U.S. Army Research Laboratory ATTN: AMSRL-OP-CI-AD, Tech Publishing 2800 Powder Mill Rd. Adelphi, MD 20783-1145	1	Director U.S. Army TRADOC Analysis Command ATTN: ATRC-WSR White Sands Missile Range, NM 88002-5502
2	Commander U.S. Army Armament Research, Development, and Engineering Center ATTN: SMCAR-IMI-I Picatinny Arsenal, NJ 07806-5000	1	Commandant U.S. Army Field Artillery School ATTN: ATSF-CSI Ft. Sill, OK 73503-5000
2	Commander U.S. Army Armament Research, Development, and Engineering Center ATTN: SMCAR-TDC Picatinny Arsenal, NJ 07806-5000	(Class. only) 1	Commandant U.S. Army Infantry School ATTN: ATSH-CD (Security Mgr.) Fort Benning, GA 31905-5660
1	Director Benet Weapons Laboratory U.S. Army Armament Research, Development, and Engineering Center ATTN: SMCAR-CCB-TL Watervliet, NY 12189-4050	(Unclass. only) 1	Commandant U.S. Army Infantry School ATTN: ATSH-CD-CSO-GR Fort Benning, GA 31905-5660
(Unclass. only) 1	Commander U.S. Army Rock Island Arsenal ATTN: SMCRI-IMC-RT/Technical Library Rock Island, IL 61299-5000	1	WL/MNOI Eglin AFB, FL 32542-5000  <u>Aberdeen Proving Ground</u>
1	Director U.S. Army Aviation Research and Technology Activity ATTN: SAVRT-R (Library) M/S 219-3 Ames Research Center Moffett Field, CA 94035-1000	2	Dir, USAMSAA ATTN: AMXSY-D AMXSY-MP, H. Cohen
		1	Cdr, USATECOM ATTN: AMSTE-TC
		1	Dir, ERDEC ATTN: SCBRD-RT
		1	Cdr, CBDA ATTN: AMSCB-CI
		1	Dir, USARL ATTN: AMSRL-SL-I
		10	Dir, USARL ATTN: AMSRL-OP-CI-B (Tech Lib)

<u>No. of Copies</u>	<u>Organization</u>
1	Ernst Mach Institute ATTN: A. J. Stulp Eckerstrasse 4 D-7800 Freiburg i. Br. WEST GERMANY
3	IABG ATTN: H. J. Raatschen W. Schittke F. Scharppf Einsteinstrasse 20 D-8012 Ottobrun B. Muenchen GERMANY
1	Royal Armament R&D Establishment ATTN: I. Cullis Fort Halstead Sevenoaks, Kent TN14 7BJ ENGLAND
1	Centre d'Etudes de Gramat ATTN: SOLVE Gerald 46500 Gramat FRANCE
2	Defense Research Establishment Suffield ATTN: C. Weickert D. Mackay Ralston, Alberta, T0J 2N0 Ralston CANADA
1	Defense Research Establishment Valcartier ATTN: N. Gass P.O. Box 8800 Courcellette, PQ, G0A 1R0 CANADA
1	Canadian Arsenals, LTD ATTN: P. Pelletier 5 Montee des Arsenaux Villie de Gardeur, PQ, J5Z2 CANADA

## USER EVALUATION SHEET/CHANGE OF ADDRESS

This Laboratory undertakes a continuing effort to improve the quality of the reports it publishes. Your comments/answers to the items/questions below will aid us in our efforts.

1. ARL Report Number ARL-MR-51 Date of Report April 1993
2. Date Report Received \_\_\_\_\_
3. Does this report satisfy a need? (Comment on purpose, related project, or other area of interest for which the report will be used.) \_\_\_\_\_  
\_\_\_\_\_  
\_\_\_\_\_
4. Specifically, how is the report being used? (Information source, design data, procedure, source of ideas, etc.) \_\_\_\_\_  
\_\_\_\_\_  
\_\_\_\_\_
5. Has the information in this report led to any quantitative savings as far as man-hours or dollars saved, operating costs avoided, or efficiencies achieved, etc? If so, please elaborate. \_\_\_\_\_  
\_\_\_\_\_  
\_\_\_\_\_
6. General Comments. What do you think should be changed to improve future reports? (Indicate changes to organization, technical content, format, etc.) \_\_\_\_\_  
\_\_\_\_\_  
\_\_\_\_\_  
\_\_\_\_\_

### CURRENT ADDRESS

\_\_\_\_\_  
Organization

\_\_\_\_\_  
Name

\_\_\_\_\_  
Street or P.O. Box No.

\_\_\_\_\_  
City, State, Zip Code

7. If indicating a Change of Address or Address Correction, please provide the Current or Correct address above and the Old or Incorrect address below.

### OLD ADDRESS

\_\_\_\_\_  
Organization

\_\_\_\_\_  
Name

\_\_\_\_\_  
Street or P.O. Box No.

\_\_\_\_\_  
City, State, Zip Code

(Remove this sheet, fold as indicated, staple or tape closed, and mail.)